

Recent development and applications in electrodes for URFC

Junjie Chen*, Deguang Xu

School of Mechanical and Power Engineering, Henan Polytechnic University, Jiaozuo, Henan, China

*E-mail address: comcjj@163.com, comcjj@yahoo.com

ABSTRACT

The design of electrodes for URFC (unitised regenerative polymer electrolyte fuel cells) requires a delicate balancing of transport media. Gas transport, electrons and protons must be carefully optimised to provide efficient transport to and from the electrochemical reaction sites. This review is a survey of recent literature with the objective to identify common components and design and assembly methods for URFC electrodes, focusing primarily on the development of a better performing bifunctional electrocatalyst for the oxygen reduction and water oxidation. Advances in unitised regenerative fuel cells study have yielded better performing oxygen electrocatalysts capable of improving energy efficiency with longer endurance and less performance degradation over time. Fuel cells using these electrocatalyst have a possible future as a source of energy.

Keywords: URFC; Regenerative fuel cell; Electrocatalyst; Water electrolysis; PEMFC; manufacturing methods; Thin-film electrodes; Gas diffusion layer

1. INTRODUCTION

Today energy consumers of various countries are heavily dependent on air polluting fossil fuels, and with the present production rate, our energy reservoirs could be emptied in less than a couple of hundred years. The environmental situation looks even more critical if we consider a scenario where coal becomes the main resource and the energy consumption per capita in heavily populated developing countries continues to increase at the same rate as today. So far around two billion people in the world do not have access to electricity [1]. Providing such a number of people with electricity will have a major effect on the environment if fossil fuels are used.

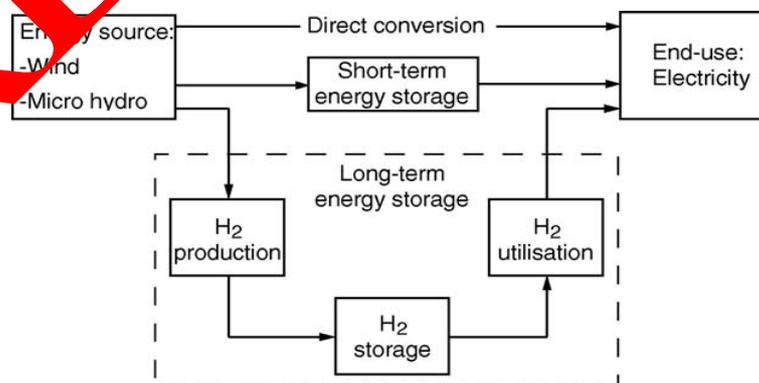


Figure 1. Schematic of energy conversions with hydrogen as a possible long-term storage.

The frightening situation described above could to, some extent be avoided by providing remote areas with renewable energy technologies such as biomass, photovoltaics and wind turbines [2]. However, wind energy is intermittent resources, i.e. the energy availability changes from hour to hour, from day to night and from season to season. This uncertainty in energy supply could however be eliminated by connecting a local energy storage system to the production unit [3]. To some extent conventional batteries have so far been used for this purpose, but the storage cost increases significantly with storage capacity. Some scientists believe that a promising alternative to batteries would be energy storage by hydrogen, which is a pollution-free, flexible energy carrier, see Fig. 1.

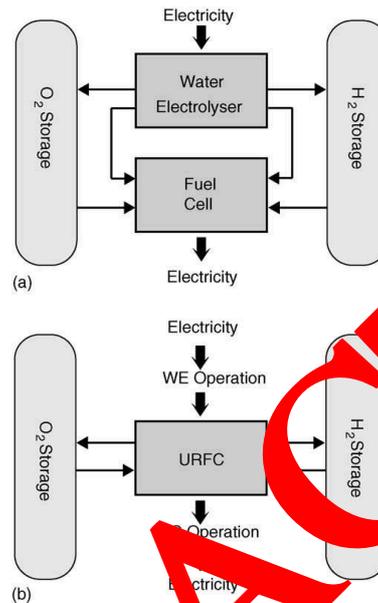


Figure 2. Concept of (a) regenerative fuel cell (RFC) and (b) unitised regenerative fuel cell (URFC).

A possible storage system for the conversion of electrical energy consists of a hydrogen production unit, a storage medium and a unit which converts the chemical energy stored in the hydrogen back to electricity (with help from oxygen or air) [4]. Such a system is preferably connected to a renewable energy source, such as solar or wind, which provides an electrolyser cell with enough energy to split water into hydrogen and oxygen. The gases are either stored or used directly in a fuel cell. In a fuel cell the opposite reaction to electrolysis takes place, i.e. hydrogen and oxygen (or air) are recombined to produce electricity, heat and water [5]. A system like this, with both an electrolyser and a fuel cell, is called a regenerative fuel cell (RFC). A much smaller and compact unit, see Fig. 2, is the unitised regenerative fuel cell (URFC). In the URFC the electrolyser and fuel cell are combined into one unit and only one of the two modes can be operated at one time. Usually the electrolyser is operated first to produce the hydrogen and oxygen, which are stored and later supplied back to the same unit when desired, which then operates as a fuel cell. Thus, a URFC is a simpler and more compact system than the RFC and it uses only one electrochemical cell [6].

Typical storage media for hydrogen and oxygen gases are either under conventional pressure vessels or in metal hydrides. Metal and liquid hydrides, such as FeTi and methanol or cyclohexane, respectively, and adsorbed carbon compounds are the principal methods of bonding hydrogen chemically [7]. They are the safest methods of storage as no hydrogen will be released in the event of an accident, but they are bulky and heavy and additional energy is also needed to release the stored hydrogen again. One of the most recent and exciting

advances has been the announcement of carbon nanofibre technology. This may have the capacity to store up to 70% of hydrogen by weight and would be a promising storage device to be used in conjunction with a lightweight URFC system [8].

Another promising technology is self-pressurising electrolyzers, which are used to supply compressed hydrogen and oxygen. This process could reduce or eliminate conventional pressure tanks all together depending on what pressure level is needed. This would be a more efficient system and a simpler and less expensive solution [9].

The key technology in the development of the PEM URFC is the fabrication of active electrocatalysts for both the oxygen reduction and the water oxidation at the oxygen electrode. The bifunctional electrocatalyst must also be resistant to anodic corrosion during the water electrolysis reaction. Several studies have reported on noble metals and metal oxides, including PtIrO₂ and PtRuO₂, as possible catalysts for the URFC oxygen electrode [10].

Recently, there has been added interest in the solid oxide regenerative fuel cell (SORFC) and its higher potential for energy storage efficiency compared to lower temperature systems [11]. Solid oxide electrolyzers show a much lower overpotential than, for example, the PEM electrolyser at standard pressure and 850 °C compared to 80 °C. The higher operating temperature of the SORFC makes it ideal as a candidate for on-grid and off-grid distributed energy storage and possibly as energy storage device for airships and submarines with its thermal energy produced. It would not be ideal on any smaller scale were ambient temperature and pressure would be the main requirements, such a system would be more suited to use the polymer electrolyte membrane URFC [12].

2. URFC

2.1. Polymer electrolyte membrane

The solid membrane in unitised regenerative polymer electrolyte membrane (PEM) fuel cells is usually a perfluorosulfonic acid polymer. This is a polytetrafluoroethylene (PTFE, trade name Teflon) chain with the chains terminating in an SO₃H group. It is the hydrogen on this sulfonate group that dissociates from the polymer when wet and appears as protons in the solution; polymer acids have the advantage that the anion (-SO₃⁻ tail) is fixed in the electrolyte rather than dissolved [13].

One common PEM is Nafion, a polymer developed by DuPont in the 1960s for use as a separator in the chlor-alkali industry and now used for other industrial electrochemical purposes. Polymer electrolyte membranes can be made extremely thin, less than 50 μm, making for densely packed stacks and, consequently, high power densities. The thinness of the PEM also means high conductance and low ohmic resistance losses [14].

Another proton exchange membrane, the Dow membrane, is also a promising candidate for the URFC but testing thereof has not been found in the literature [15].

2.2. Catalyst layer

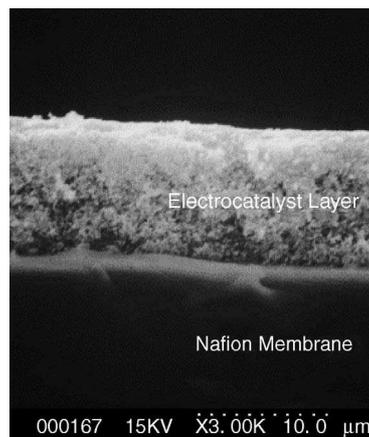


Figure 3. Scanning electron micrograph (SEM) of a cross-section of an electrocatalyst assembly.

The catalyst layer in a unitised regenerative fuel cell is in direct contact with the membrane and the gas diffusion layer, see Fig. 3. This layer is either applied directly to the membrane or to the gas diffusion layer with the aim to get the catalyst particles as close as possible to the polymer electrolyte membrane. Catalyst layers for URFCs have always been an important part of the development of efficient regenerative cells [16]. Historically, Pt black has been used as the sole catalyst but later study has recognised several other suitable catalysts, including iridium (Ir), ruthenium (Ru) and rhodium (Rh). Study has also been concentrated on lowering the high Pt content in URFC catalyst layers (typically 3-7 mg cm⁻²) and later study has shown that catalyst loadings as low as 0.4 mg cm⁻² is possible with the help of a supported bifunctional catalyst.

2.3. Electrode manufacture

URFC electrode designs have typically used proven and tested methods to produce the electrode-membrane-electrode interface. Most widely used is the transfer print technique followed by hot press (and/or roll press) of the design for more intimate contact of active materials. Application techniques like spraying, painting and casting are also used. Other emerging promising methods are chemical reduction, electrodeposition and sputter deposition, but these will not be discussed here in any depth [17].

2.4. Gas diffusion layer

The gas diffusion layer (GDL) in URFCs ensures an even distribution and removal of reactants and products from the electrode area. It is also acting as the electrical conductor during transport of electrons to and from the catalyst layer [18]. The GDL is also an important factor in the water management of the cell, balancing between the different properties of the fuel cell and the water electrolyser. It also plays a vital role in the hydration of the polymer electrolyte membrane.

3. URFC MEMBRANE-ELECTRODE ASSEMBLIES

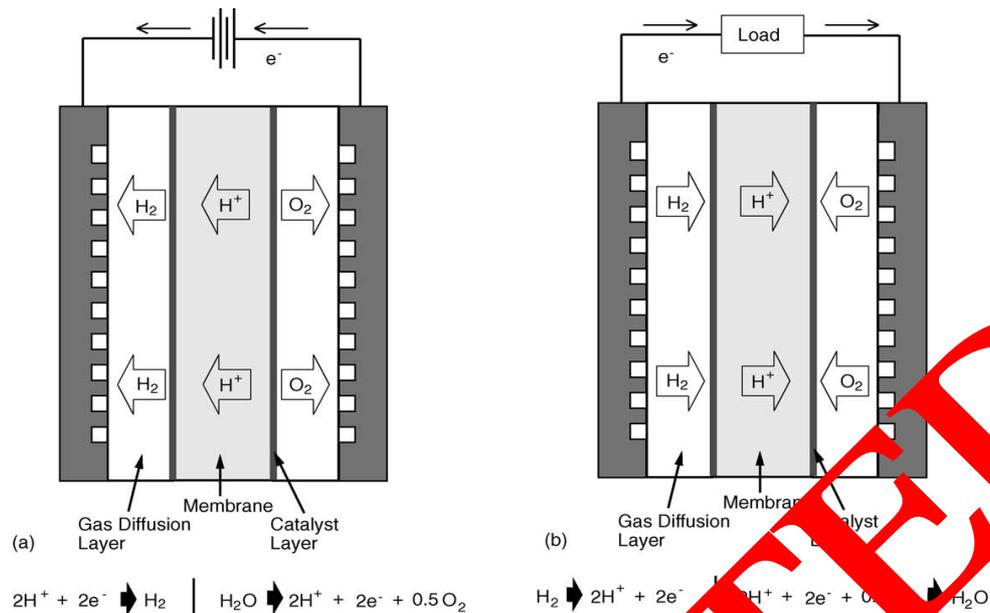


Figure 4. Schematic of a URFC with reactions, (a) PEM electrolyser and (b) PEM fuel cell.

There are two problems encountered when designing electrode structures for URFC systems [19]. For PEM fuel cells, highly hydrophobised carbon paper or carbon cloth is usually adopted as the gas diffusion layer and electrode materials, however, they cannot be used as the GDL of a URFC for the following two reasons: firstly, the carbon materials tend to corrode at high potentials on the oxygen electrode side during the water electrolysis operation; secondly, GDLs have to achieve an appropriate balance between the hydrophobic and hydrophilic properties for both the fuel cell and water electrolysis operations, as shown in Fig. 4. The fuel cell operation requires that the oxygen GDL have a hydrophobic property to prevent water flooding, on the other hand, water electrolysis requires that the GDL have a hydrophilic property to supply water to the oxygen electrode. Several methods have been demonstrated to overcome these problems by using specially designed electrodes with complex multi-layer structures or membranes with internal fluid passages [20]. However, while these methods overcome one of the basic problems, neither of these approaches leads to a cell (stack) with adequate performance for use in applications.

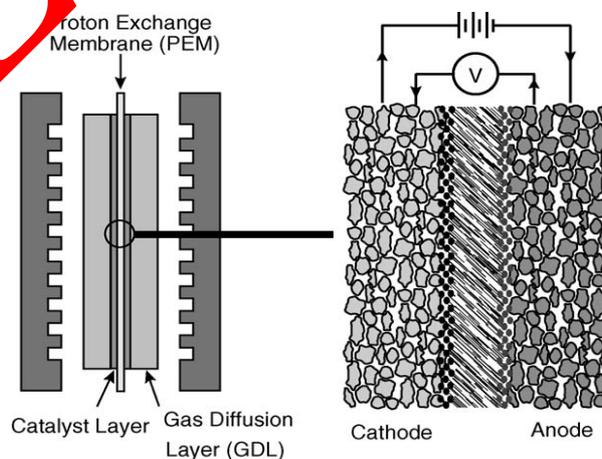


Figure 5. Membrane-electrode assembly of typical PEM URFC.

In a typical design of a URFC, each electrode is always in contact with the same gas, hydrogen or oxygen, and the electrical polarisation of the cell (or stack) is reversed when the system changes function, see Fig. 4. Therefore, if the unit is operating as an electrolyser, the oxygen electrode is the anode and the hydrogen electrode is the cathode [21]. If the unit is operating as a fuel cell, the oxygen electrode is the cathode and the hydrogen electrode is the anode [22]. It is therefore important when designing electrodes for URFCs that they are both designed so that they do not degrade when operated in an oxidising environment (Fig. 5).

3.1. URFC hydrogen electrode

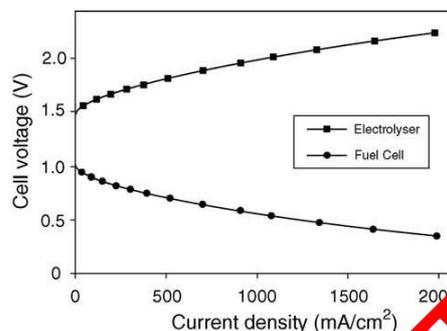


Figure 6. Schematic of PEM electrolyser and fuel cell voltage vs current density.

There have been many studies on suitable electrocatalysts for URFCs, however the majority of them focus on the development of a suitable catalyst for the oxygen electrode and only briefly discuss the formation of the hydrogen electrode [23]. This is more than likely due to the favourable kinetics of hydrogen on platinum. On the hydrogen electrode and hydrogen evolution is known to perform best with platinum as the catalyst material. High current densities are realised at low overpotentials, see typical current-voltage graph Fig. 6. There is no mass transport limitation and the only restriction of the hydrogen evolving electrode is its sensitivity to poisoning. Some early studies use platinum on carbon (Pt/C) as the catalyst source for the hydrogen oxidation and evolution, but more recent work uses unsupported platinum black as the electrocatalyst [24].

3.2. URFC oxygen electrode

An important part of the development of an oxygen electrode is the choice of electrocatalyst. It is well known that the best electrocatalyst for oxygen reduction, platinum (in its reduced form) is not the best catalyst for water oxidation and oxygen evolution. Early studies by Cruz et al. [25], showed that apart from platinum, iridium oxide (IrO_2) would be a good candidate for oxygen evolution, even though a relatively poor candidate as oxygen reduction catalyst. Mixed or alloyed with platinum, Pt/IrO_2 proved to function well as a bifunctional electrode catalyst. The study also identified RuO_x to be a good potential catalyst for the oxygen evolution of a bifunctional oxygen electrode. It was also found that the catalyst $\text{Na}_x\text{Pt}_3\text{O}_4$ could be a possible candidate, but further investigation would be needed. Further testing of these catalysts showed results of 0.723 V in the fuel cell mode and 1.587 V in the electrolyser mode when using Pt/Pt-IrO_2 operated at 500 mA cm^{-2} . When using $\text{Pt/Pt-Na}_x\text{Pt}_3\text{O}_4$ as the electrocatalyst, the performance was measured as 0.740 V in the fuel cell mode and 1.697 V in electrolyser mode, a significant improvement on the Pt/IrO_2 electrode.

Abdullah and Kamarudin [26] used Pt black and IrO_2 as the oxygen electrode catalysts and found that 50 wt.% Pt and 50 wt.% IrO_2 performed well with very low catalyst loadings

(0.4 mg cm^{-2}). A thin-film catalyst layer structure was used, as opposed to previously used two-layer electrode structures, in order to decrease the limitations imposed on mass transport and ohmic limitations, by the two-layer electrode structure. Performance of the cell was 0.7 V in the fuel cell mode and 1.71 V in the electrolyser mode, at 400 mA cm^{-2} , $80 \text{ }^\circ\text{C}$ and 0.3 MPa and ambient pressure, respectively.

Xiao et al. [27] investigated the use of IrO_2 and Pt black as feasible substitutes to the commonly used Pt/C electrodes in PEMFC and it was found that the oxidation and reduction reactions (ORR) of oxygen were more likely on a Pt/ IrO_2 electrode, due to higher combined surface area compared to Pt black. The overall performance of the cell seemed to change with the amount of IrO_2 in the electrode. In fuel cell mode, the performance decreased with increased amount and in electrolyser mode, the performance was found to increase with the amount of IrO_2 . A conversion efficiency of 49% was reached at a current of 500 mA , but further testing showed an increase in the efficiency to 51%, which is lower than that of a typical battery. The IrO_2 content of the electrodes was optimised at 10-30 mol%.

Vivanpatarakij et al. [28] looked even further into the nature of a suitable bifunctional electrocatalyst for URFC's by screening 715 unique combinations of five elements (Pt, Ru, Os, Ir and Rh) using combinatorial chemistry. The ternary catalyst Pt₄Ru₄Ir_{0.5} (subscripts indicate atomic ratios) was identified to be the most efficient and stable catalyst for the oxygen electrode in a URFC system. The study showed that the addition of Ru to the Pt/Ir electrode increased the reaction rate by stabilising the surface atomic oxygen bonds.

3.3. Electrocatalyst supports

The importance of the catalyst support has been well recorded [29]. Characteristically, a support provides a physical surface for dispersion of small metal particles, which is necessary to achieve high surface area. Additional roles would typically be wettability and to provide good electronic conductivity. In fuel cell systems, carbon has generally been used as the innocent conductive support with minor interference with the supported metal particles and the surface functional groups. Carbon as supports was primarily introduced to reduce the noble metal loadings within the cells. Loadings have to date been reduced from ca. 7 to 0.1 - 0.2 mg cm^{-2} in hydrogen/oxygen fuel cells. However, oxidation of carbon at the fuel cell cathode limits the practical lifetime of the supported catalyst [30]. High potentials at the oxygen electrode in URFC during electrolysis mode lead to severe carbon corrosion.

Work has been reported on the use of electronically conductive carbon substitutes in fuel cell systems, these include boron carbide, tantalum boride, titanium carbide and some perovskite compounds [31]. Conductive oxide supports, particularly reduced titanium oxides and titanium-niobium oxide composites have been used in electrolysers and are important candidates for use in the oxygen electrodes of URFCs.

Park et al. [32] recently examined potential electrocatalysts and oxide supports. They looked at combinations of the catalysts Pt, Ir, Ru, Os and Rh on one or more of the following three oxides: Ebonex (primarily composed of Ti_4O_7), phase-pure microcrystalline Ti_4O_7 and $\text{Ti}_{0.9}\text{Nb}_{0.1}\text{O}_2$ a doped rutile compound. They measured stability and activity on the different catalysts and found that the highest levels of activity and stability were in the Pt-Ru-Ir ternary region at compositions near $\text{Pt}_4\text{Ru}_4\text{Ir}$. Due to the short-lived electrochemical stability of Ti_4O_7 and Ebonex at oxygen evolution conditions above 1.6 V versus RHE in $0.5 \text{ M H}_2\text{SO}_4$ (aq), there is a gradual loss of current associated with these supports. In addition, Ebonex and Ti_4O_7 underwent thermal oxidation at temperatures above $400 \text{ }^\circ\text{C}$ and it was found that support composed of $\text{Ti}_{0.9}\text{Nb}_{0.1}\text{O}_2$ was resistant to both electrochemical and thermal oxidation.

Flick et al. [33] have developed a direct deposition of Pt catalyst onto the solid membrane using a thin-film catalyst layer impregnated with polypyrrole (ppy). Polypyrrole proved to improve the fabrication of the catalyst layer directly on to the surface of the Nafion

membrane and overall improved the performance of the URFC. Results showed a fuel cell performance of 190 mA cm^{-2} at 0.695 V (with a catalyst loading of 0.38 mg cm^{-2}) and 250 mA cm^{-2} at 2.0 V at ambient pressure and $60 \text{ }^\circ\text{C}$ for the water electrolyser.

Alternatively, other oxygen reduction electrocatalysts can be used in substitution for, or in combination with, platinum [34]. An important consideration is that the oxygen reduction electrocatalyst must be stable to degradation under oxygen evolution conditions while the URFC is operating in fuel cell mode.

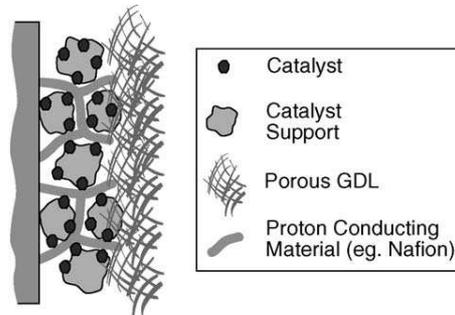


Figure 7. Schematic of typical URFC membrane-electrode interface

Additionally, an effective electrode has each of the catalyst particles in contact with at least one other electronically conducting particle so that it has a continuous electronic path to the electrical conducting current collector. It also has a continuous ionic network linking each catalyst particle to the membrane (see Fig. 7). Some investigators have developed complex arrangements with a variable internal structure to achieve these properties. It would be an advantage for an electrode to have a simple arrangement, with the same gross composition used throughout the volume of the electrode, making it simpler to fabricate.

3.4. Gas diffusion layer

In addition to selecting an electrocatalyst for the development of URFC electrodes, it is vital to develop a porous, conductive gas diffusion layer to ensure an even distribution and removal of reactants and products from the entire electrode area to ensure uninterrupted electrical contact between current collector/distributor and electrodes [35]. In conventional PEM fuel cells, this is commonly carried out by a porous carbon matrix structure, commonly carbon paper or carbon cloth, this is however not suitable for long-term use in a URFC electrode structure due to oxidation of carbon during the water electrolysis. Even though the oxidation rate is slow over a considerable amount of time in use, enough carbon will have been consumed to reduce electrical contact in the MEA and thus affect the performance of the cell.

The metal material(s) of the GDL provides both strength for the electrode structure as well as a continuous electrical contact between the current collecting structure and the electrodes [36]. The porous nature of the GDL material must also ensure effective diffusion of each reactant gas and water to the catalyst on the membrane-electrode assembly. The structure of the GDL must also allow the gas to spread out so that the gas and water will be in contact with the entire surface area of the membrane. In a conventional PEMFC the GDL is usually wet-proofed to assist in the water management in the MEA of the cell. In URFCs, as mentioned earlier, the GDL has to achieve an appropriate balance between the hydrophilic and hydrophobic properties for both fuel cell and the water electrolyser.

The gas diffusion layer is most likely to be a woven metal cloth, expanded metal sheet; perforated metal sheets or metal foam and useful materials for the GDL of a URFC include titanium, zirconium, hafnium, niobium and tantalum. Doddathimmaiah and Andrews [37] looked at using titanium, which is a corrosion-resistive and electron-conductive material in highly cathodic and acidic environments, as the GDL for URFCs. In the study, a variety of titanium GDLs coated with different amounts of hydrophilic solution, polytetrafluoroethylene, were prepared and tested. The study found that hydrophilic content of the hydrogen GDL did not effect the cell performance, on the other hand, the amount of hydrophilic content of the oxygen GDL changed the performance of the URFC significantly. It showed that a loading of 16 mg cm^{-2} was the most appropriate on the oxygen GDL, however more testing would be needed to evaluate practical durability.

Oxidation resistant alloys are also useful materials for GDLs, such as stainless steels, Inconels (predominately nickel and chromium) and Hastelloys (predominately nickel). A lot of use are precious metals such as platinum, gold, ruthenium, iridium and palladium. Other metals and alloys such as nickel, aluminium and copper are useful as well, as long as they are protected from oxidation through coatings.

Another approach to this type of structure is a gas diffusion electrode (GDE). In a GDE the catalyst (with or without support material) and the GDL is combined into one structure. The advantage of this type of structure is that the porous conductive matrix structure of the GDL can be incorporated into the electrocatalyst layer of the MEA or vice versa. This would lead to a significantly thinner and lighter structure, having the same functions and support as the individual layer structures, and also a significant reduction in manufacturing costs.

4. URFC MEA MANUFACTURING METHODS

Conventional membrane-electrode assemblies for PEMFC are usually comprised of a Pt/C catalyst layer and a gas diffusion layer. But the conventional membrane-electrode assembly is not commonly applied to water electrolysis because the gas diffusion layer may inhibit the diffusion of reactants and products. Due to this reason, most MEAs used in URFC are constructed of two-layer structure electrodes consisting of the membrane and a gas diffusion electrode. The GDE is most commonly a thin-film electrocatalyst layer and consists of a catalyst, a proton conducting polymer and a solvent.

Typically, URFC gas diffusion electrodes are hot-pressed (following transfer printing) to each side of the membrane to form the MEA [38]. However, the catalyst loading in the roll-press method is very high ($8\text{-}10 \text{ mg cm}^{-2}$), thus other methods like the transfer print technique, followed by hot-press is beginning to take over, see Fig. 8. In the transfer print technique, a thin catalyst layer containing the ionomer as the resin (binder) is first applied to a Teflon blank sheet to form a stencil and then transferred to the membrane by hot-pressing where after the press is over the Teflon sheet is peeled away from the newly made MEA. A similar method, developed by the same study group, applied the catalyst directly to the membrane. The catalyst, suspended in an ink containing an alcoholic solvent, was painted onto a dry membrane and allowed to dry on a vacuum table before being turned over and the second catalyst layer was applied. In order to allow intimate contact with the membrane, high pressing temperatures and pressures were employed. However, the membrane in its proton-conducting H^+ form could not withstand these harsh processing conditions so instead a more rigid form of the membrane is used, the ion exchange so called Na^+ form. The MEA is then converted back to its proton-conducting H^+ form by boiling the membrane in sulfuric acid.

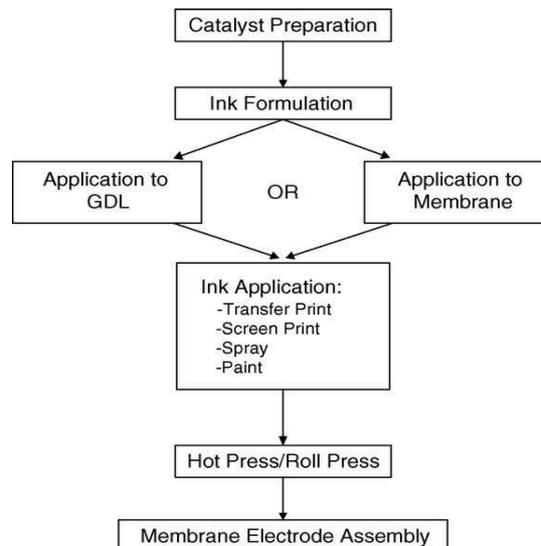


Figure 8. Flow diagram of URFC MEA assembly

Other techniques, widely used in the manufacturing of PEM MEA and promising candidates in the URFC field are screen-printing, chemical reduction method, impregnation techniques and sputter deposition but still to date, the transfer and/or the hot-press methods are the most widely used within the URFC field, but these methods used need to be developed further to make hydrogen energy systems, based on PEM technology, realistic contestants to modern day batteries.

5. CONCLUSION

This report outlined a review of recent advances made in the field of electrodes and electrocatalysts for unitised regenerative PEM fuel cells. It was found that the most common approach to manufacture of the electrode structure for the URFC is a thin-film approach using the transfer print technique for the catalyst layer followed by hot pressing of the catalyst layer and the solid polymer membrane to form the MEA of URFC. The ability of the interface to conduct protons from the membrane into the catalyst layer and the catalyst sites is crucial, and thin-film layered structures have shown promise for low catalyst loadings with adequate performance. Other promising application techniques for URFC MEAs are sputter deposition and chemical reduction, but more study needs to be done into these fields if these particular type of fuel cell are to be a viable replacement technology to batteries.

Reference

- [1] Zhu F., Andreasen S.J., Kær S.K., Yu D., Analysis of accelerated degradation of a HT-PEM fuel cell caused by cell reversal in fuel starvation condition. *International Journal of Hydrogen Energy* 40(6) (2015) 2833-2839.
- [2] Shukla S., Domican K., Karan K., Bhattacharjee S., Secanell M., Analysis of Low Platinum Loading Thin Polymer Electrolyte Fuel Cell Electrodes Prepared by Inkjet Printing. *Electrochimica Acta* 156(0) (2015) 289-300.
- [3] Zhang L., Zhu X., Kashima H., Li J., Ye D.-d., Liao Q., Regan J.M., Anolyte recirculation effects in buffered and unbuffered single-chamber air-cathode microbial fuel cells. *Bioresource Technology* 179(0) (2015) 26-34.

- [4] Hong T., Chen F., Xia C., Barium carbonate nanoparticle as high temperature oxygen reduction catalyst for solid oxide fuel cell. *Electrochemistry Communications* 51(0) (2015) 93-97.
- [5] Wang J., Barriers of scaling-up fuel cells: Cost, durability and reliability. *Energy* 80(0) (2015) 509-521.
- [6] Altmann S., Kaz T., Friedrich K.A., Bifunctional electrodes for unitised regenerative fuel cells. *Electrochimica Acta* 56(11) (2011) 4287-4293.
- [7] Banan R., Bazylak A., Zu J., Combined effects of environmental vibrations and hygrothermal fatigue on mechanical damage in PEM fuel cells. *International Journal of Hydrogen Energy* 40(4) (2015) 1911-1922.
- [8] Giddey S., Badwal S.P.S., Kulkarni A., Munnings C., A comprehensive review of direct carbon fuel cell technology. *Progress in Energy and Combustion Science* 32(3) (2011) 360-399.
- [9] Grigoriev S.A., Millet P., Dzhus K.A., Middleton H., Saetre T., Fateev V.N., Design and characterization of bi-functional electrocatalytic layers for application in PEM unitized regenerative fuel cells. *International Journal of Hydrogen Energy* 35(10) (2010) 5070-5076.
- [10] Grigoriev S.A., Millet P., Poremsky V.I., Fateev V.N., Development and preliminary testing of a unitized regenerative fuel cell based on PEM technology. *International Journal of Hydrogen Energy* 36(6) (2011) 4164-4168.
- [11] Abd El Monem A.A., Azmy A.M., Mahmoud M., Effect of process parameters on the dynamic behavior of polymer electrolyte membrane fuel cells for electric vehicle applications. *Ain Shams Engineering Journal* 5(1) (2014) 75-84.
- [12] Roca-Ayats M., García G., Galante J.L., Peña M.A., Martínez-Huerta M.V., Electrocatalytic stability of Pt/C based supported Pt₃Ir nanoparticles for unitized regenerative fuel cells. *International Journal of Hydrogen Energy* 39(10) (2014) 5477-5484.
- [13] Nasani N., Ramasamy D., Andrews J., Perez J., Fagg D.P., Electrochemical behaviour of Ni-BZO and Ni-BZr cermet anodes for Protonic Ceramic Fuel Cells (PCFCs) - A comparative study. *Electrochimica Acta* 154(0) (2015) 387-396.
- [14] Bozbağ S.E., Çimüşoğlu M., Yilmaztürk S., Ayala C.J., Aindow M., Deligöz H., Erkey C., Electrochemical performance of fuel cell catalysts prepared by supercritical deposition: effect of different precursor conversion routes. *The Journal of Supercritical Fluids* 97(0) (2015) 154-164.
- [15] Zhuo X., Sui S., Zhang J., Electrode structure optimization combined with water flooding modes for Bi-Functional Unitized Regenerative Fuel Cells. *International Journal of Hydrogen Energy* 38(11) (2013) 4792-4797.
- [16] Andrews J., Seif Mohammadi S., Towards a 'proton flow battery': Investigation of a reversible PEM fuel cell with integrated metal-hydride hydrogen storage. *International Journal of Hydrogen Energy* 39(4) (2014) 1740-1751.
- [17] Gurrola M.P., Gutiérrez J., Rivas S., Guerra-Balcázar M., Ledesma-García J., Arriaga L.G., Evaluation of the corrosion of Sb-doped SnO₂ supports for electrolysis systems. *International Journal of Hydrogen Energy* 39(29) (2014) 16763-16770.

- [18] Elmer T., Worall M., Wu S., Riffat S.B., Fuel cell technology for domestic built environment applications: State of-the-art review. *Renewable and Sustainable Energy Reviews* 42(0) (2015) 913-931.
- [19] Meng X., Yan W., Yang N., Tan X., Liu S., Highly stable microtubular solid oxide fuel cells based on integrated electrolyte/anode hollow fibers. *Journal of Power Sources* 275(0) (2015) 362-369.
- [20] Deleebeeck L., Arenillas A., Menéndez J.A., Kammer Hansen K., Hybrid direct carbon fuel cell anode processes investigated using a 3-electrode half-cell setup. *International Journal of Hydrogen Energy* 40(4) (2015) 1945-1958.
- [21] Siracusano S., Baglio V., Stassi A., Ornelas R., Antonucci V., Aricò A.S., Investigation of IrO₂ electrocatalysts prepared by a sulfite-couplex route for the O₂ evolution reaction in solid polymer electrolyte water electrolyzers. *International Journal of Hydrogen Energy* 36(13) (2011) 7822-7831.
- [22] Kim K.N., Kang J.H., Lee S.G., Nam J.H., Kim C.-J., Lattice Boltzmann simulation of liquid water transport in microporous and gas diffusion layers of polymer electrolyte membrane fuel cells. *Journal of Power Sources* 278(0) (2015) 703-717.
- [23] Wittstadt U., Wagner E., Jungmann T., Membrane electrode assemblies for unitised regenerative polymer electrolyte fuel cells. *Journal of Power Sources* 145(2) (2005) 555-562.
- [24] Matos B.R., Isidoro R.A., Santiago E.I., Tavares A.C., Ferlauto A.S., Muccillo R., Fonseca F.C., Nafion-titanate nanotubes composite prepared by in situ crystallization and casting for direct ethanol fuel cells. *International Journal of Hydrogen Energy* 40(4) (2015) 1859-1867.
- [25] Cruz J.C., Baglio V., Siracusano S., Ornelas R., Arriaga L.G., Antonucci V., Aricò A.S., Nanosized Pt/IrO₂ electrocatalyst prepared by modified polyol method for application as dual function oxygen electrode in unitized regenerative fuel cells. *International Journal of Hydrogen Energy* 37(7) (2012) 5508-5517.
- [26] Abdullah N., Kamarudin S., Carbon dioxide in fuel cell technology: An overview. *Journal of Power Sources* 275(0) (2015) 109-118.
- [27] Xiao J., Zhang W., Zhang C., Chen B., Pu J., Jian L., Oxidation of MnCu_{0.5}Co_{1.5}O₄ spinel coated SUS304 alloy interconnect in anode and cathode atmospheres for intermediate temperature solid oxide fuel cell. *International Journal of Hydrogen Energy* 40(4) (2015) 1868-1875.
- [28] Vivanpatarakij S., Bouache F., Assabumrungrat S., Performance of an improved combination unit of Pd-membrane methane steam reformer and intermediate temperature solid oxide fuel cell (C-Pd-ITSOFC). *International Journal of Hydrogen Energy* 40(4) (2015) 1894-1901.
- [29] Guo F., Fu G., Zhang Z., Performance of mixed-species biocathode microbial fuel cells using saline mustard tuber wastewater as self-buffered catholyte. *Bioresource Technology* 180(0) (2015) 137-143.
- [30] Yazdi H., Alzate-Gaviria L., Ren Z.J., Pluggable microbial fuel cell stacks for septic wastewater treatment and electricity production. *Bioresource Technology* 180(0) (2015) 258-263.
- [31] Jamil S.M., Othman M.H.D., Rahman M.A., Jaafar J., Ismail A.F., Li K., Recent fabrication techniques for micro-tubular solid oxide fuel cell support: A review. *Journal of the European Ceramic Society* 35(1) (2015) 1-22.

- [32] Park S., Lee J.-W., Popov B.N., A review of gas diffusion layer in PEM fuel cells: Materials and designs. *International Journal of Hydrogen Energy* 37(7) (2012) 5850-5865.
- [33] Flick S., Dhanushkodi S.R., Mérida W., Transport phenomena in polymer electrolyte membrane fuel cells via voltage loss breakdown. *Journal of Power Sources* 280(0) (2015) 97-106.
- [34] Gabbasa M., Sopian K., Fudholi A., Asim N., A review of unitized regenerative fuel cell stack: Material, design and research achievements. *International Journal of Hydrogen Energy* 39(31) (2014) 17765-17778.
- [35] Cruz J.C., Rivas S., Beltran D., Meas Y., Ornelas R., Osorio-Monreal G., Ortiz-Lizasoain L., Ledesma-García J., Arriaga L.G., Synthesis and evaluation of ATO as a support for IrO₂ in a unitized regenerative fuel cell. *International Journal of Hydrogen Energy* 37(18) (2012) 13522-13528.
- [36] Zhou N., Yang C., Tucker D., Pezzini P., Traverso A., Transfer function development for control of cathode airflow transients in fuel cell gas turbine hybrid systems. *International Journal of Hydrogen Energy* 40(4) (2015) 1987-1979.
- [37] Doddathimmaiah A., Andrews J., Theory, modelling and performance measurement of unitised regenerative fuel cells. *International Journal of Hydrogen Energy* 34(19) (2009) 8157-8170.
- [38] Dihrab S.S., Sopian K., Alghoul M.A., Sulaiman M.Y., Review of the membrane and bipolar plates materials for conventional and unitized regenerative fuel cells. *Renewable and Sustainable Energy Reviews* 13(6-7) (2009) 1663-1668.

(Received 28 January 2015; accepted 09 February 2015)